PB89-236392

Identification of CaSO4 Formed by Reaction of CaO and SO2

Acurex Corp., Research Triangle Park, NC

Prepared for:

Environmental Protection Agency, Research Triangle Park, NC

1989

U.S. Department of Commerce
National Technical Information Service
NTIS

AEERL-P-526

TECHNICAL REPORT DATA
(Please read Instructions on the reverse before comple

1. REPORT NO. EPA/600/J-89/007	2.	3. PB89-236392
4. TITLE AND SUBTITLE Identification of $CaSO_4$ Formed by Reaction of CaO and SO_2		5. REPORT DATE 6. PERFORMING ORGANIZATION CODE
7. AUTHOR(S) B.K. Gullett (EPA/AEERL) and K.R. Bruce (Acurex)		8. PERFORMING ORGANIZATION REPORT NO.
9. PERFORMING ORGANIZATION NAME AND ADDRESS Acurex Corporation P.O. Box 13109 Research Triangle Park, North Carolina 27709		10. PROGRAM ELEMENT NO. 11. CONTRACT/GRANT NO. 68-02-4701
12. SPONSORING AGENCY NAME AND ADDRESS EPA, Office of Research and Development Air and Energy Engineering Research Laboratory Research Triangle Park, NC 27711		13. TYPE OF REPORT AND PERIOD COVERED Journal article; 10/88-3/89 14. SPONSORING AGENCY CODE EPA/600/13

15. SUPPLEMENTARY NOTES AEERL project officer is Brian K. Gullett, Mail Drop 4, 919/541-1534. AIChE J.

16. ABSTRACT The article discusses the XRD-determination of the identity of CaSO4, formed by the reaction between CaO and SO2, and the support of that determination by density measurements with helium pycnometry. The anhydrous CaSO4 compound formed has an orthorhombic crystal structure and an analytically calculated density of 2.98 g/cu cm, versus the JCPDS reported value of 2.995 g/cu cm. The product of this reaction, formed during calcium-based sorbent injection for SO2 removal from coal-fired power plants, has largely been assumed to have a density of 2.61 g/cu cm. Since reaction models must incorporate the product density in determining the rate of sorbent pore blockage or filling, correct identification of the reaction product is crucial.

17. KEY WORDS AND DOCUMENT ANALYSIS

a. DESCRIPTORS	b. IDENTIFIERS/OPEN ENDED TERMS	c. COSATI Field/Group
Pollution	Pollution Control	13B
Calcium Sulfates	Stationary Sources	07B
Calcium Oxides		
Sulfur Dioxide		
Sorbents		11G
Porosity		14G
Mathematical Models		12A

REPRODUCED BY
U.S. DEPARTMENT OF COMMERCE
NATIONAL TECHNICAL INFORMATION SERVICE
SPRINGFIELD, VA. 22161

18. DISTRIBUTION STATEMENT Release to Public	19. SECURITY CLASS *(This Report)* Unclassified	21. NO. OF PAGES 15
	20. SECURITY CLASS *(This page)* Unclassified	22. PRICE

EPA Form 2220-1 (9-73)

EPA/600/J-89/007

IDENTIFICATION OF $CaSO_4$ FORMED BY REACTION OF CaO AND SO_2

Brian K. Gullett*
United States Environmental Protection Agency
Air and Energy Engineering Research Laboratory
Research Triangle Park, North Carolina 27711

NTIS is authorized to reproduce and sell this report. Permission for further reproduction must be obtained from the copyright owner.

Kevin R. Bruce
Acurex Corporation
Research Triangle Park, North Carolina 27709

Keywords: density, porosity, calcium sulfate, sorbents, sulfur dioxide

*To whom correspondence should be addressed.

Introduction

The injection of calcium-based sorbents into coal-fired boilers for reaction with, and reduction in the levels of, sulfur dioxide (SO_2) in the flue gas has undergone considerable research and development. Significant effort has also been made in developing models for the overall reaction

$$CaO + SO_2 + 1/2\ O_2 \longleftrightarrow CaSO_4$$

in order to better predict the effects of system and sorbent variables upon performance. Development of internal surface area (Borgwardt and Bruce, 1986) and pore structure (Hartman and Coughlin, 1974) is necessary for measurable reaction to occur. Further, since the calcium sulfate ($CaSO_4$) product has a larger molar volume than the reactant, calcium oxide (CaO), the extent of pore volume development may control the levels of reaction. The molar volume of $CaSO_4$ is related to its density. One of the earlier references (Hartman and Coughlin, 1974) to the $CaSO_4$ product density uses the molar volume value of 52.2 cm^3/mol or 2.6 g/cm^3. This leads to a product/reactant expansion ratio,

$$Z = \nu_{CaSO_4} / \nu_{CaO},$$

of 52.2/16.9, or 3.09. Use of this particular handbook value (Weast, 1968) of density (or its associated Z value) has continued in subsequent papers (Hartman and Coughlin, 1976; Ramachandran and Smith, 1977; Hartman et al., 1978; Bhatia and Perlmutter, 1981); Sotirchos and Yu, 1985; Reyes and Jensen,

1987; Borgwardt et al., 1987; Kocaefe et al., 1987; Simons and Garman, 1986; Yu and Sotirchos, 1987). One instance (Hartman and Trnka, 1980) is noted where the value of 2.97 g/cm^3 (45.8 cm^3/mol) has been used, cited from an unidentified handbook. This last case results in a Z value of 2.71. Apparently the earliest documented reference questioning the commonly accepted molar volume value is by Dam-Johansen (1987). This work determined a molar volume of 48.06 cm^3/mol from a model comparison with experimental porosity/conversion data. Deviation from the inferred 46.0 cm^3/mol (2.96 g/cm^3) value was attributed to experimental errors and an insufficient model.

The value of Z is particularly significant for modelling the sulfation reaction. Since the larger volume product fills or blocks sorbent pore volume, slowing or stopping the reaction, the ability of models to appropriately simulate laboratory reaction results is contingent upon proper determination of the physical parameters involved. To this end, analyses to identify the form of the $CaSO_4$ product and determine its density (molar volume) were performed.

Experimental Method

Samples of calcium hydroxide [$Ca(OH)_2$] and calcium carbonate ($CaCO_3$) were reacted at 800°C for 5 min supported on quartz wool in a fixed-bed reactor. Preheated reactor gas [0.3 % SO_2, 5 % oxygen (O_2), balance nitrogen (N_2)] at 23 l/min and standard temperature and pressure (STP) passed through

the sample bed, converting the sample to the reactive CaO form and then reacting it to form $CaSO_4$ (further details of similar experimental procedures are available in Borgwardt and Bruce, 1986). The samples were analyzed by x-ray diffraction (XRD), helium pycnometry, atomic absorption spectroscopy (AA), ion chromatography (IC), and thermogravimetric analysis (TGA).

XRD analyses for compound identification were performed on a diffractometer with a copper Kα target source running at 50 kV and 40 mA. The entrance aperture was 1.0 degrees and the detector slit was 0.05 degrees. Spectra were identified by computer comparison with the Joint Committee for Powder Diffraction Spectra (JCPDS) spectral files. Density measurements were performed on a helium pycnometer which measures solid sample volume. Calibration with manufacturer-supplied standards ensured instrument accuracy and precision. TGA measurements determined the weight percent of trace $Ca(OH)_2$ and $CaCO_3$ in the sample product, while AA and IC measurements determined the weight percent of $SO_4^{=}$ and Ca^{++}, respectively.

Results and Discussion

Fig. 1 shows the XRD spectrum of the sample product formed from the reaction of $Ca(OH)_2$ with SO_2. This spectrum is overlaid with the spectrum for CaO to account for incomplete conversion to product $CaSO_4$. The XRD spectrum from the $CaCO_3$ sample product was nearly identical to that from the $Ca(OH)_2$ sample product, except for slightly higher CaO peaks. The higher CaO peaks

are due to the longer time for calcination of the $CaCO_3$ than dehydration of the $Ca(OH)_2$. For both calcium-based precursors, the analysis identified the sample product to be calcium sulfate anhydrite, JCPDS registry No. 37-1496. This is an orthorhombic crystal structure with a density of 2.995 g/cm^3 (45.46 cm^3/mol). Fig. 1 shows that the CaO and $CaSO_4$ spectra account for all major and minor peaks present in the sample spectrum, affirming the identity of the $CaSO_4$ product.

The identification of this $CaSO_4$ form, having a higher density than previously ascribed to the $CaSO_4$ product, led to further efforts to verify the density. Since the XRD spectra identified the same $CaSO_4$ for both $CaCO_3$ and $Ca(OH)_2$ sorbents, helium pycnometer analyses were done only on the reaction product of $Ca(OH)_2$. These analyses were combined with the TGA, AA, and IC results (accounting for 99.5 % of the sample product mass) to determine the sample density. The results from five trials indicate a compound with a mean density of 2.98 g/cm^3 (standard deviation of 0.08).

Fig. 2 shows the impact of this density determination upon pore volume-limited sulfation of the CaO and compares it with the more commonly used density value. The molar volume ratio Z, 2.70, calculated from the density determined in this work, suggests that considerably more reaction can occur within the porous matrix than with the commonly cited value of 3.09. For $Ca(OH)_2$ that develops its theoretical porosity during dehydration to CaO, its theoretical porosity, ϵ, is

$$\nu_{CaO} / \nu_{Ca(OH)_2} = 16.9 \text{ cm}^3/\text{mol} / 33.1 \text{ cm}^3/\text{mol} = 0.510.$$

Likewise, for calcination of $CaCO_3$, ϵ is

$$\nu_{CaO} / \nu_{CaCO_3} = 16.9 \text{ cm}^3/\text{mol} / 36.9 \text{ cm}^3/\text{mol} = 0.458.$$

These molar volume values are derived from Weast (1968). The maximum conversion based upon complete pore filling of the porosity by the larger volume product can be calculated from

$$X_s = \epsilon / (Z-1)(1-\epsilon)$$

Thus, the maximum expected conversion for $Ca(OH)_2$ is 61.2 % and for $CaCO_3$ is 49.7 %.

While this Z value helps to account for some of the exceedances of the X_s values noted experimentally (Kocaefe et al., 1987; Gullett et al., 1988), it does not fully account for reaction levels (up to 90 % conversion) observed by Borgwardt and Bruce (1986). Nonetheless, the magnitude of the density change will have a significant effect upon sulfation models that incorporate reaction limitations based upon pore filling or blocking.

Conclusions

The identity of $CaSO_4$ formed by the reaction between CaO and SO_2 has been determined by XRD and supported by density measurements with helium pycnometry. The anhydrous $CaSO_4$ compound formed has an orthorhombic crystal structure and an analytically calculated density of 2.98 g/cm^3 versus the JCPDS reported value of 2.995 g/cm^3. The product of this reaction, formed during calcium-based sorbent injection for SO_2 removal from coal power plants, has largely been assumed to have a density of 2.61 g/cm^3. Since reaction models must incorporate the product density in determining the rate of sorbent pore blockage or filling, correct identification of the reaction product is crucial.

Acknowledgement

The authors are grateful for the assistance of Per Alvfors from The Royal Institute of Technology, Sweden; the XRD analyses of Frank E. Briden, U. S. Environmental Protection Agency, Air and Energy Engineering Research Laboratory; and the laboratory work of John W. Foster and Paul W. Groff, Acurex Corporation.

Notation

ϵ	original porosity, unitless
ν_{CaO}	molar volume of CaO, cm^3/mol
ν_{CaSO_4}	molar volume of $CaSO_4$, cm^3/mol
X_s	conversion to product based on complete pore volume filling, %
Z	molar volume ratio of $CaSO_4/CaO$, unitless
2θ	angle of detector to x-ray beam, degrees

Literature Cited

Bhatia, S. K., and D. D. Perlmutter, "The Effect of Pore Structure on Fluid-Solid Reactions: Application to the SO_2-Lime Reaction," AIChE J., 27, 226 (1981).

Borgwardt, R. H., and K. R. Bruce, "Effect of Specific Surface Area on the Reactivity of CaO with SO_2," AIChE J., 32, 239 (1986).

Borgwardt, R. H., K. R. Bruce, and J. Blake, "An Investigation of Product-Layer Diffusivity for CaO Sulfation," I & E C Research, 26, 1993 (1987).

Dam-Johnasen, K., "Sulphur Dioxide Retention on Dry Chalk," Ph.D. Thesis, Technical University of Denmark, Lyngby (1987).

Gullett, B. K., J. A. Blom, and R. T. Cunningham, "Porosity, Surface Area, and Particle Size Effects of CaO Reacting With SO_2 at 1100°C," React. Solids, 6, 263 (1988).

Hartman, M., and R. W. Coughlin, "Reaction of Sulfur Dioxide with Limestone and the Influence of Pore Structure," I & E C Process Des. Dev., 13, 248 (1974).

Hartman, M., and R. W. Coughlin, "Reaction of Sulfur Dioxide with Limestone and the Grain Model," AIChE J., 22, 490 (1976).

Hartman, M., J. Pata, and R. W. Coughlin, "Influence of Porosity of Calcium Carbonates on Their Reactivity with Sulfur Dioxide," I & E C Process Des. Dev., 17, 411 (1978).

Hartman, M., and O. Trnka, "Influence of Temperature on the Reactivity of Limestone Particles With Sulfur Dioxide," Chem. Eng. Sci., 35, 1189 (1980).

Kocaefe, D., D. Karman, and F. R. Steward, "Interpretation of the Sulfation Rate of CaO, MgO, and ZnO with SO_2 and SO_3," AIChE J., 33, 1835 (1987).

Ramachandran, P. A., and J. M. Smith, "A Single Pore Model for Gas-Solid Noncatalytic Reactions," AIChE J., 23, 353 (1977).

Reyes, S., and K. F. Jensen, "Percolation Concepts in Modelling of Gas-Solid Reactions -- III. Application to Sulphation of Calcined Limestone," Chem. Eng. Sci., 42, 565 (1987).

Simons, G. A., and A. R. Garman, "Small Pore Closure and the Deactivation of the Limestone Sulfation Reaction," AIChE J., 32, 1491 (1986).

Sotirchos, S. V., and H-C Yu, "Mathematical Modelling of Gas-Solid Reactions with Solid Product," Chem. Eng. Sci., 40, 2039 (1985).

Yu, H-C., and S. V. Sotirchos, "A Generalized Pore Model for Gas-Solid Reactions Exhibiting Pore Closure," AIChE J., 33, 382 (1987).

Weast, R. C., Handbook of Chemistry and Physics, 49th ed., The Chemical Rubber Co., Cleveland, Ohio (1968).

LIST OF FIGURES

Fig 1 XRD spectra of $Ca(OH)_2$ sulfation sample with CaO spectra (JCPDS No. 37-1497) and $CaSO_4$ anhydrite spectra (JCPDS No. 37-1496).

Fig. 2 Maximum conversion based upon complete filling of initial porosity with Z = 3.09 and 2.70.

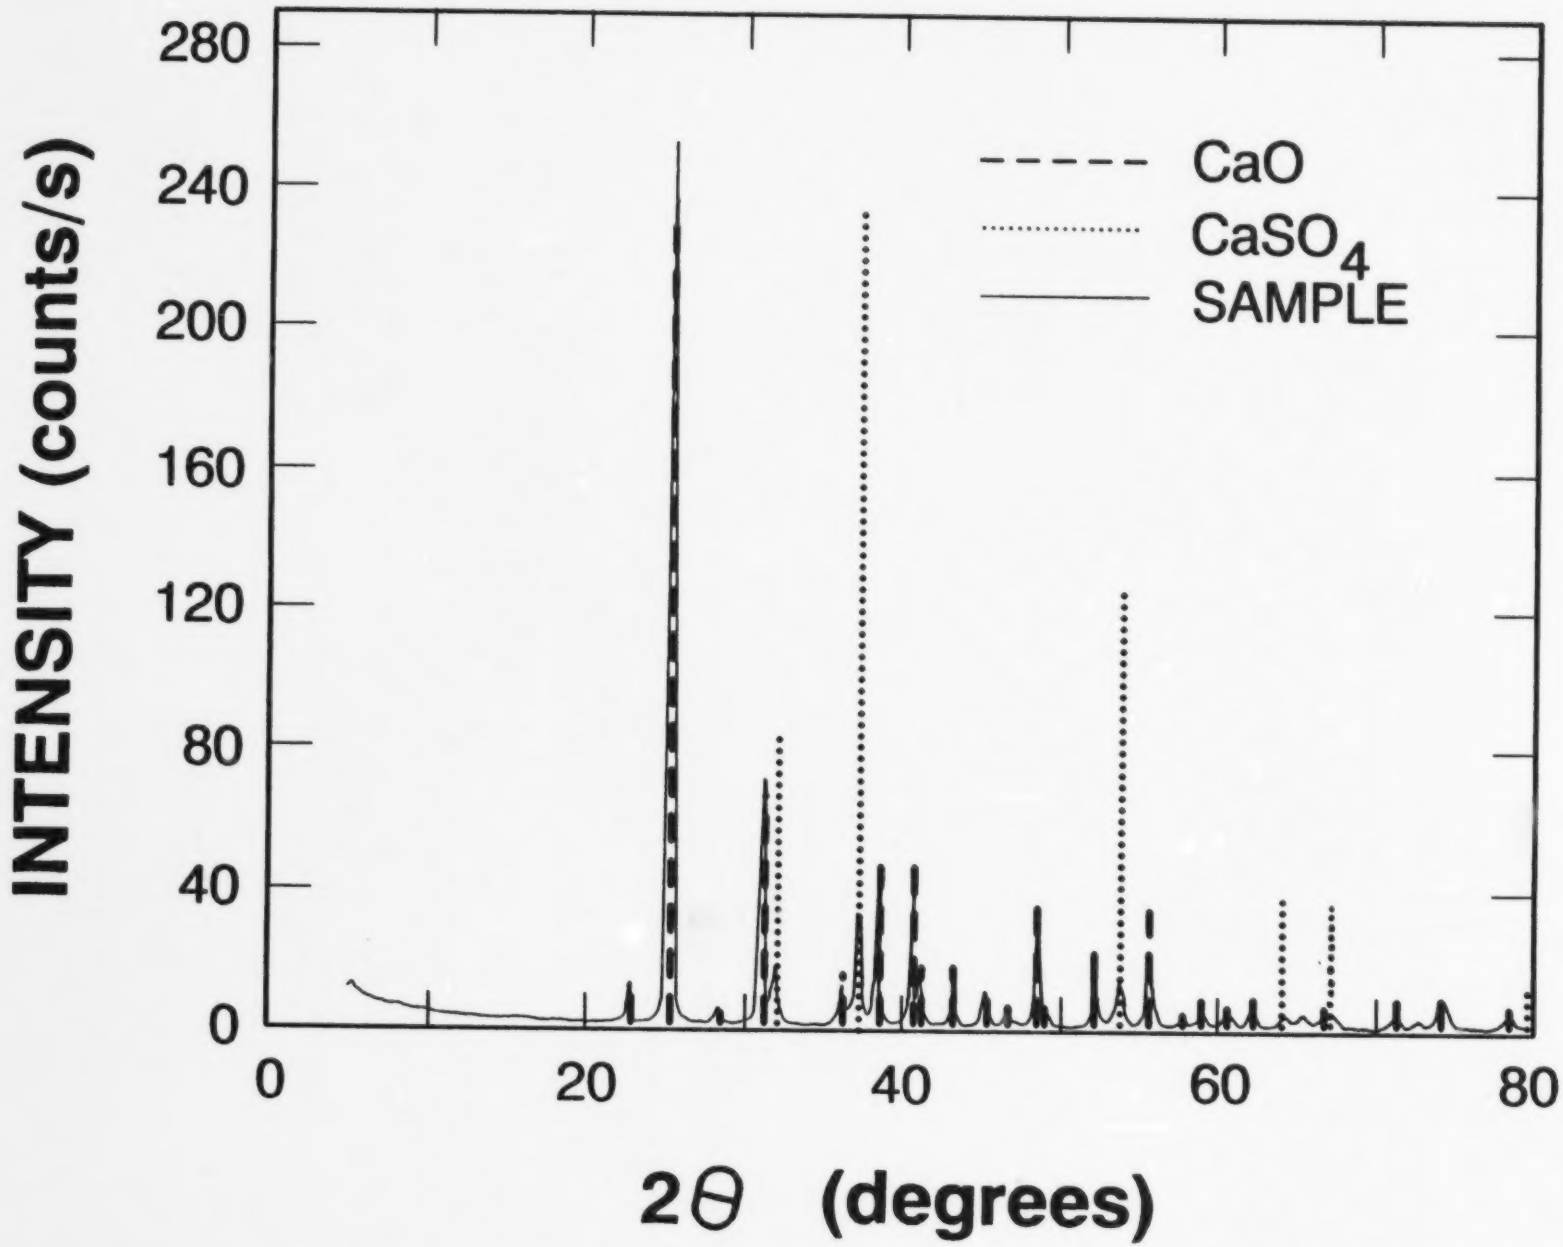
INTENSITY (counts/s)
280
240
200
160
120
80
40
0
0
20
40
60
80
2θ (degrees)
CaO
CaSO4
SAMPLE

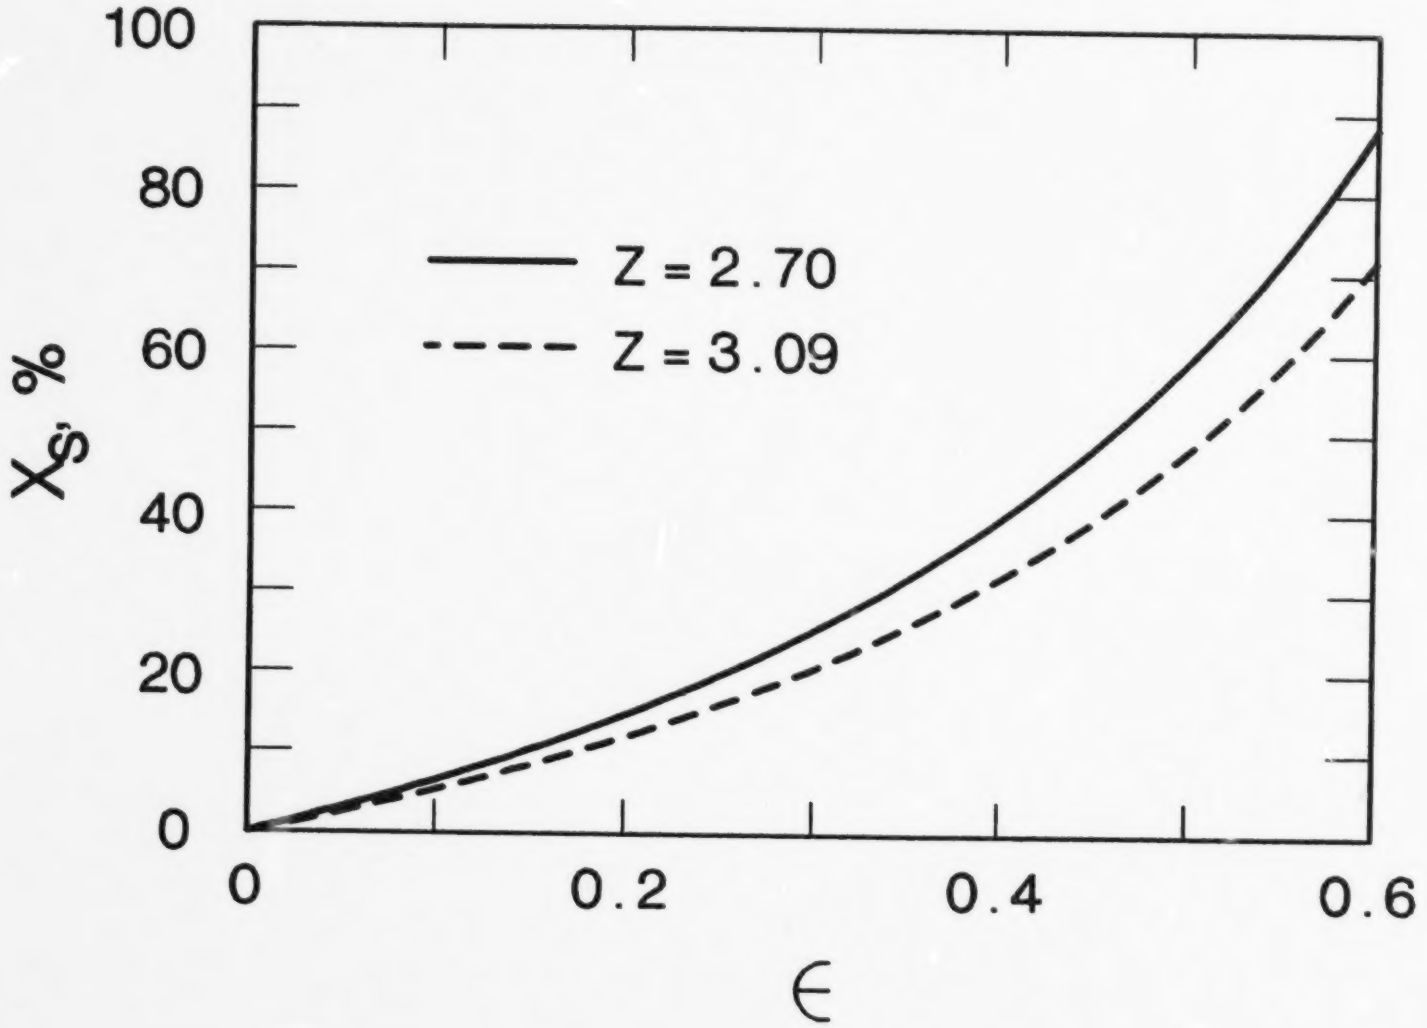
100
80
60
40
20
0
X_S, %
Z = 2.70
Z = 3.09
0
0.2
0.4
0.6
ϵ